

S-76LTH

COVERED ARC WELDING ELECTRODE
FOR HIGH TENSILE STEEL(490MPa)
AND LOW TEMPERATURE SERVICE STEEL

2020.12



❖ Specification

AWS A5.5	E7016-G
EN ISO 2560-A	E42 6 Z1Ni B 1 2 H5
ZIS Z 3211	E4916-N1 AP L

❖ Applications

Single or multi pass welding for various low temperature service steel such as offshore sector, LPG storage tank, and heat exchanger etc.

❖ Characteristics on Usage

S-76LTH is a basic and low hydrogen type electrode for all position welding. It provide excellent notch toughness at low temperature down to -60°C (-76°F) and CTOD properties at -40°C (-40°F) temperature..

❖ Note on Usage

1. Dry the electrodes at $350\sim 400^{\circ}\text{C}$ ($662\sim 752^{\circ}\text{F}$) for 30~60 minutes before use.
2. Keep the arc as short as possible, and avoid large width weaving.
3. Adopt back step method or strike the arc on a small steel plate prepared for this particular purpose to prevent blow-hole at the arc starting.
4. Use the wind screen against strong wind.




Mechanical properties & Chemical compositions of Deposited metal

❖ Welding Conditions

Measurement method	: AWS A5.5
Diameter	: 3.2mm(1/8in) , 4.0mm(5/32in). 5.0mm(3/16in)
Welding position	: Flat (1G-PA)
Welding Current	: 3.2mm(1/8in) = 140Amp, AC, 12passes – 6 layers 4.0mm(5/32in) = 180Amp, AC, 16passes – 8 layers 5.0mm(3/16in) = 200Amp, AC, 14passes – 6layers
Interpass Temp.	: 105~175°C (221~347°F)
Test plate	: EH36 (groove shape as below)

❖ Groove configuration

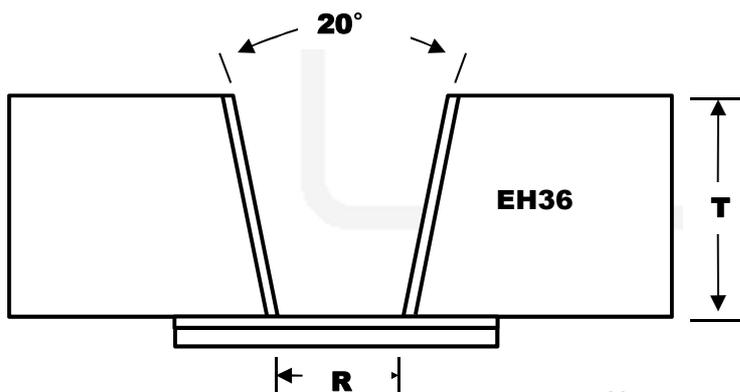

Notes

- : 3.2mm ; T=13mm, R=13mm
- : 4.0mm ; T=20mm, R=16mm
- : 5.0mm ; T=20mm, R=19mm



Mechanical properties & Chemical compositions of Deposited metal

❖ Mechanical properties of deposited metal in as-welded condition

Size mm(in)	Tensile Test Results			CVN Impact Test J (ft·lbs)	
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-45°C (-49°F)	-60°C (-76°F)
3.2(1/8)	503(73,400)	582(84,400)	31.2	166(123)	144(106)
4.0(5/32)	514(74,500)	580(84,100)	30.0	163(120)	91(67)
5.0(3/16)	468(67,900)	559(81,100)	33.6	173(128)	95(70)
AWS Spec.	≥ 390(57,000)	≥ 490(71,000)	≥ 22	Not specified	

❖ Mechanical properties of deposited metal after PWHT condition (625°C X 8hr)

Size mm(in)	Tensile Test Results			CVN Impact Test J (ft·lbs)	
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-45°C (-49°F)	-60°C (-76°F)
3.2(1/8)	463(67,100)	555(80,500)	32.0	197(145)	135(100)
4.0(5/32)	439(63,700)	526(76,300)	30.0	140(103)	129(95)
5.0(3/16)	420(60,900)	512(74,200)	28.0	169(125)	114(84)
AWS Spec.	≥ 400(58,000)	≥ 490(71,000)	≥ 22	Not specified	

❖ Chemical compositions of deposited metal (wt%)


Size	C	Si	Mn	P	S	Ni	Ti	B
3.2(1/8)	0.08	0.28	1.10	0.012	0.007	0.52	0.019	0.0029
4.0(5/32)	0.07	0.30	1.18	0.010	0.004	0.47	0.022	0.0025
5.0(3/16)	0.07	0.28	1.14	0.014	0.003	0.50	0.025	0.0027
AWS Spec.	-	≥0.80*	≥1.00*	≤ 0.03	≤ 0.03	≥0.50*	-	-

* In order to meet the alloy requirement of the "G" group, the undiluted weld metal shall have the minimum of at least one of the elements least on this table.



Mechanical properties for one-sided welding of pipes

❖ Welding Conditions

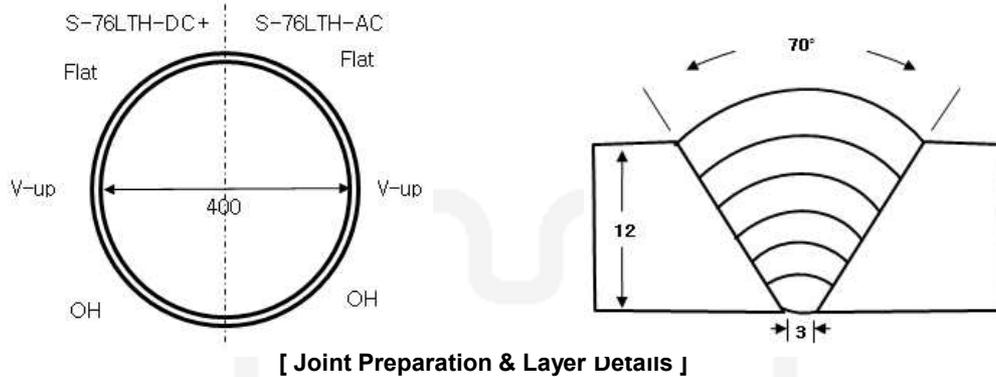

- * Base metal : ASTM A333 Gr.6
- * Wire diameter : 3.2/4.0 mm
- * Polarity : AC /DCEP
- * Welding parameter :
 - 1~2 layer : GTAW(ER-70S-3) 2.4mm, 10~15kJ / cm
 - 3 layer : S-76LTH 3.2mm, 20~30kJ / cm
 - 4~6 layer : S-76LTH 4.0mm , 30~50 kJ/cm
- * Welding Position : all position (except vertical down position)

❖ Test result

Polarity	Position	CVN Impact Test J (ft·lbs)			
		-45°C (-49°F)			
		X1	X2	X3	Avg.
AC	Flat (PA)	83(61)	81(60)	95(70)	85(63)
	V-Up (PF)	120(89)	105(77)	115(85)	113(83)
	OH (PE)	78(58)	83(61)	76(56)	79(58)
DC+	Flat (PA)	88(65)	91(67)	95(70)	91(67)
	V-Up (PF)	125(92)	118(87)	113(83)	118(87)
	OH (PE)	98(72)	96(71)	92(68)	95(70)

* S-76LTH can maintain fine micro-structure in welded metal with higher heat input(50kJ/cm), due to the specific chemical composition (0.5Ni-Ti-B).

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Absorbed Moisture contents

❖ Test Conditions

Measurement method	: AWS A4.4
Diameter	: 3.2mm(1/8in) , 4.0(5/32mm). 5.0(3/16in)
Exposed environment	: 30°C(86°F) and 80% Relative humidity (RH)
Exposed Time	: 3~12 hours (* AWS requirement is period of not less than 9 hours)
Analysis method	: Infrared Detector
Limit of moisture content	: As-Received or Reconditioned ($\leq 0.4\%$) / As-Exposed (Not specified)

❖ Test result

Size mm(in)	Absorbed moisture contents (wt%)				
	As-received	3hr	6hr	9hr	12hr
3.2(1/8)	0.033	0.033	0.233	0.328	0.633
4.0(5/32)	0.026	0.046	0.123	0.198	0.665
5.0(3/16)	0.024	0.090	0.206	0.193	0.459

Size mm(in)	Variations of moisture contents (wt%) at Re-drying 350°C(662°F) X 1 hr				
	As-received	3hr	6hr	9hr	12hr
3.2(1/8)	0.033	0.040	0.030	0.037	0.016
4.0(5/32)	0.026	0.030	0.010	0.019	0.031
5.0(3/16)	0.024	0.030	0.030	0.049	0.035

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Diffusible Hydrogen Content

❖ Test Conditions

Diameter	: 3.2mm(1/8in) , 4.0mm(5/32in). 5.0mm(3/16in)
Exposed environment	: 30°C(86°F) and 80% Relative humidity (RH)
Exposed time	: 3~12 hours
Re-drying conditions	: 350°C(662°F) X 1hr / 400°C(752°F) X 1hr
Welding current	3.2mm(1/8in) = 140Amp, AC : 4.0mm(5/32in) = 180Amp, AC 5.0mm(3/16in) = 200Amp, AC
Test method	AWS A4.3 (Gas chromatography method)

❖ Test result

Size mm(in)	Variations of Hydrogen contents (ml/100g) Re-drying 350°C(662°F) X 1hr				
	As-received	3hr	6hr	9hr	12hr
3.2(1/8)	3.21	4.77	4.61	5.92	5.07
4.0(5/32)	3.17	4.43	4.51	4.61	5.49
5.0(3/16)	3.92	4.91	4.34	6.46	9.55

Size mm(in)	Variations of Hydrogen contents (ml/100g) Re-drying 400°C(752°F) X 1hr				
	As-received	3hr	6hr	9hr	12hr
3.2(1/8)	3.21	3.32	4.08	4.56	4.69
4.0(5/32)	3.17	3.53	3.19	4.21	4.49
5.0(3/16)	3.92	4.12	4.36	4.85	4.08

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Weldability & Deposition Efficiency

❖ Weldability

Position Item	Welding	Flat (1G-PA)	V-Up (3G-PF)
Arc stability		Good	Excellent
Melting rate		Excellent	Excellent
Deposition rate		Excellent	Excellent
Resistance of spatter occurrence		Excellent	Good
Bead appearance		Excellent	Excellent
Slag detachability		Good	Good

❖ Test Conditions of Deposition Efficiency

Consumable	Base Metal		Welding conditions		
	Specification	Dimension mm(in)	Amp. (A)	Welding speed (mm/min)	Position
S-76.LTH (4.0 x 400 mm) (5/32 x 16 in)	ASTM A36	300 X 100 X12 (12 X 3.9 X 0.5)	160 (AC/DC+)	155	1G-PA

❖ Results of Deposition Efficiency

Consumable	Current & Polarity	Deposition efficiency(%)	
		For electrode	For core wire
S-76LTH 4.0 x 400 mm (5/32 x 16 in)	AC	66 ~ 70	98 ~ 105
	DC+	65 ~ 69	95 ~ 102

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Optimum Welding Condition

❖ Available sizes and Recommended Current

Diameter, mm(in)		2.6 (3/32)	3.2 (1/8)	4.0 (5/32)	5.0 (3/16)
Length, mm(in)		350(14)	350(14)	400(16)	400(16)
Recommended current range (AC or DC+)	Flat (1G-PA)	60 ~90	90 ~140	130 ~190	180 ~250
	3G (PF) & 4G,5G (PE)	50 ~80	80 ~120	120 ~170	150 ~200

❖ Authorized Approval Details

Classification	Dia. (mm)	Welding position	Grade	
			ABS	DNV-GL
AWS				
E7016-G	2.6 ~ 5.0	All (except V-Down)	5Y ,5Y400 H5	5Y, 5Y40 H5 (NV4-4L)

Notice

**This test report is made for giving general information, and it's not meaning guarantee.
Test results are changeable by several welding - parameter including base materials**

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.